



Reducing casting defects in ductile iron castings by optimized pouring system

Mustafa Murat Zor^{*1}, Serdar Kesim¹, Ferhat Tülüce¹, Alper Yoloğlu¹

¹ÇİMSATAŞ Çukurova Construction Machinery IND. TRADE. A.S. Mersin, Türkiye, [foundry@cimsatas.com](mailto:foundation@cimsatas.com)

Cite this study: Zor, M. M., Kesim, S., Tülüce, F., & Yoloğlu, A. (2023). Reducing casting defects in ductile iron castings by optimized pouring system. *Engineering Applications*, 2 (1), 26-31

Keywords

Ductile iron casting
Kalpur direct pouring system
Modelling and simulation
Casting defects
Filtration
Greensand casting

Research Article

Received: 07.12.2022

Revised: 03.01.2023

Accepted: 14.01.2023

Published: 03.02.2023



Abstract

Casting simulation technology is an most effective method to provide the predicted information on casting defects such as shrinkage, gas entrapment and non-metallic inclusions. In the study, various version pouring systems have been designed for ductile iron castings in the industrial conditions and a computer-aided design solid modeling program was used in the design of pouring systems for ductile iron castings. Pouring system for ductile iron castings and the gating system ratio of the casting part was selected as 1:3,5:2,5. The flow and solidification of the pouring systems of the casting part was simulated by using magma flow and solidification program. The study clearly shows that the kalpur direct pouring system has revealed that it plays a significant role in preventing non-metallic casting defects in ductile iron castings, such as sand, gas, and slag. In addition, it has been observed in the study that clean parts can be obtained in ductile iron castings with an effective and well-designed pouring system design. The kalpur direct pouring system is recommended to be used in ferrous based castings by FOSECO. The kalpur direct pouring system was used for the first time in ÇİMSATAŞ foundry in the ductile iron castings and the appropriate result was obtained.

1. Introduction

Casting process plays a very important role in manufacturing industry. Modern foundry engineering is a well-developed and sophisticated industry utilizing cutting-edge technologies and tools including 3D printing, robust and automated manufacturing. Despite this, the most important production technology remains the use of greensand molds poured with cast iron or steel. Major applications and uses of castings are in automobile industry, agricultural industry, construction machinery etc. [1-3].

Non-metallic inclusions defects in the casting parts effect the material properties, surface quality and machinability of cast metals, resulting in scrapped castings and or their premature failure. Oxide, sand, and slag inclusions are casting defects that are troublesome and damaging to casting performance. In carbon and low alloy steel castings, reaction between oxygen in the atmosphere and most reactive elements in deoxidized steel results in reoxidation inclusions. In ductile iron castings, the reaction of magnesium oxide and silica during magnesium treatment and further during mold filling is responsible for the formation dross inclusions [3-6].

Pouring system is one of the important design terms of ductile iron casting. And it refers to those channels through which the metal flows from the ladle to mold cavity. High casting quality depends on a reasonable pouring system design. An improper pouring system could result in turbulence, air entrapment and inclusions in the filling process [7-9].

In recent years, foundry metal filtration technology has been rising popularity in casting system for casting processes of many metals such as cast irons, steel and aluminum. Filtration technology is evolving as the demand

for defect-free, quality castings with high yield, low scrap rates and increase of low process costs. The benefit of filters, especially reticulated foam filters, besides their turbulence-reducing effect, is to prevent non-metallic inclusions such as sand and slag from entering the casting part during pouring the molten metal into the sand mold [10-12].

The kalpur direct pouring system developed by FOSECO for foundries is used in greensand molding lines and resin molding lines to obtain high part efficiency and clean casting parts. The kalpur direct pouring system includes many critical components within its own structure; exothermic feeder, ceramic foam filter, and collapsible breaker core etc. The main purpose of the kalpur direct pouring system is; reduced fettling cost, reduced non-metallic inclusions, lower turbulence related defects, improved directional solidification, good surface finish optimized yield, and increased space on the pattern plate. Parts molded with the kalpur direct pouring system can be poured with lip pouring ladle or bottom pouring ladle [12-16].

2. Material and Method

In this study, it has been aimed to develop pouring systems for ductile iron castings and to reduce casting defects by using a computer aided solid modeling program. The pouring systems designs of connecting casting part are based on the modulus and geometry of the casting part. In the study, the material of the part is determined according to the DIN EN 1563 standard and material of the casting part has been selected as GGG50. The part with two different pouring systems have been molded in the greensand molding system and casted in ÇİMSATAŞ foundry. The chemical composition of the casting part has been selected as shown in Table 1 and the image of the connecting casting part is shown in Figure 1.

Table 1. Chemical composition of the connecting casting part

Contents	% C	% Mn	% S	% P	% Si	% V	% Cu	% Mg	% Pb
Min.	3,6	0,18	0	0	2,4	0	0,29	0,03	0
Max.	3,75	0,22	0.01	0,1	3	0,02	0,31	0,06	0,02

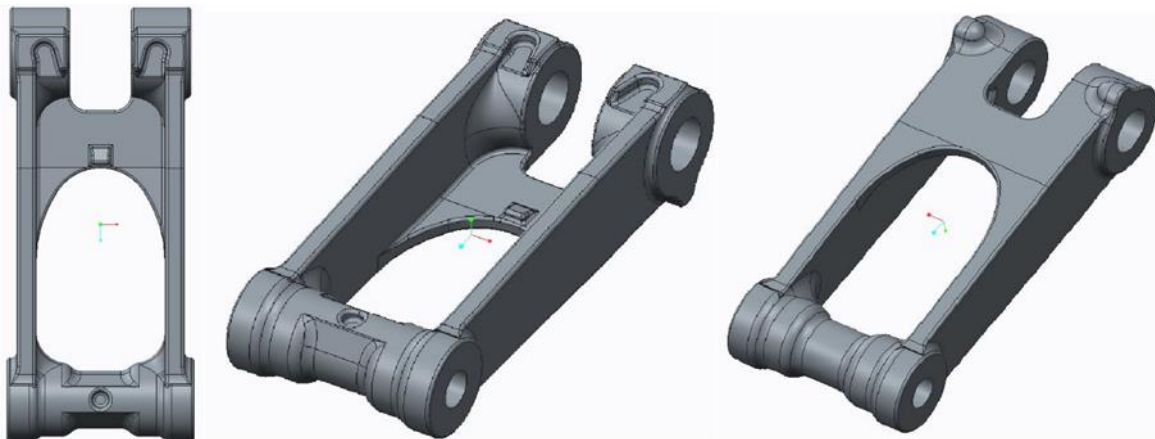


Figure 1. Schematic representation of the connecting casting part

In the first pouring system study, pouring system design of the connecting casting part is based on total gross weight of the part (total gross weight including gating system and feeders) and effective casting height. Total gross weight of the casting part is 105 kg and effective casting height is 32 cm. The gating system ratio of the casting part has been chosen as 1:3,5:2,5. Pouring system has been designed by using solid data and then, flow and solidification of the part has been simulated at 1350 °C by choosing lip pouring ladle. According to simulation results, designed pouring system has been mounted to the casting part model. The designed pouring system ratio and dimensions of the casting part are shown in Table 2 and the images of the simulation results of the casting part are shown in Figure 2.

After simulation results, one part was molded in the greensand molding system in ÇİMSATAŞ foundry and the casting has been carried out with a lip pouring ladle at 1350 °C and in 20 seconds. Total gross weight of the casting part has been detected as 105 kg. Image of the designed pouring system mounted in the part model and image of the poured part with designed pouring system is shown in Figure 3.

Table 2. Designed pouring system ratio and dimensions.

Gating system ratio	Vertical runner	Horizontal runner	Ingate
1:3,5:2,5	1	3,5	2,5
	12,56 cm ²	43,96 cm ²	17,5 cm ²

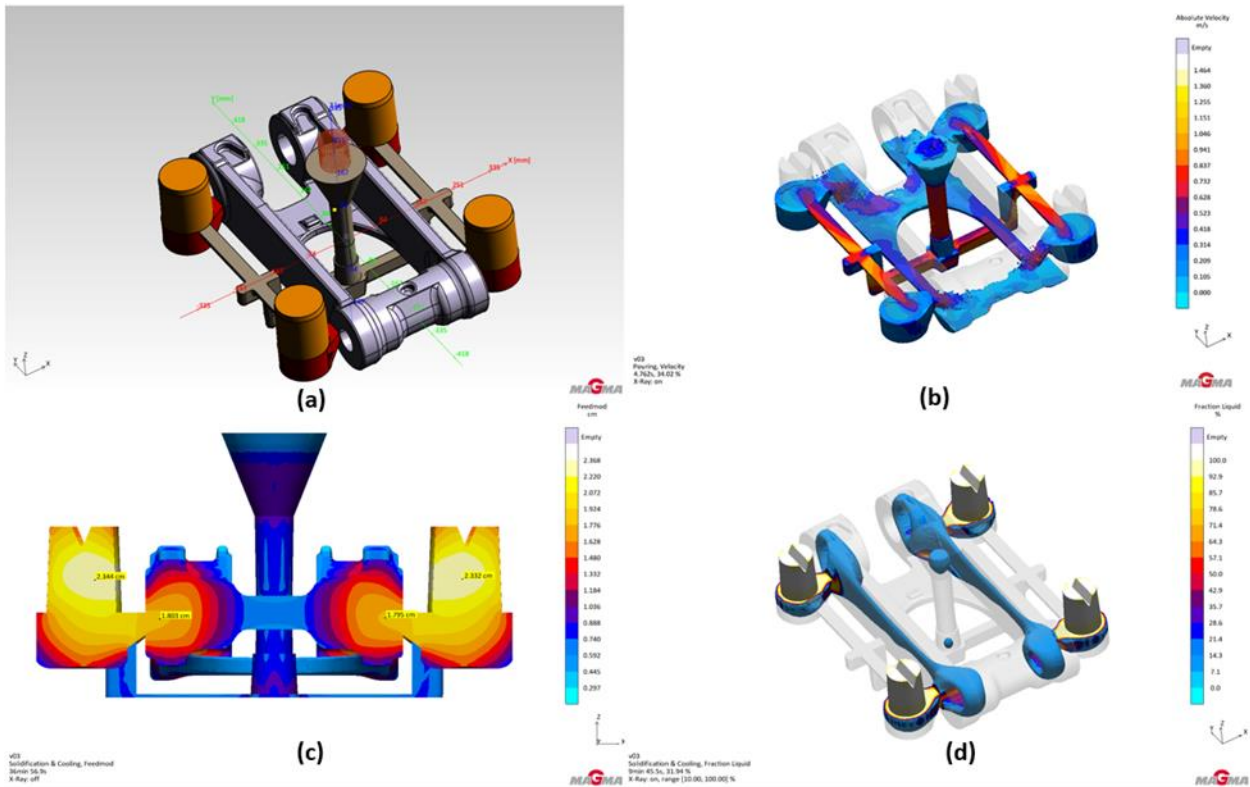


Figure 2. (a); The image of the casting part geometry, **(b);** The image of the metal flow and filling simulation of the casting part, **(c);** The image of the feeding mod of the casting part, **(d);** The image of the friction liquid mod of the casting part

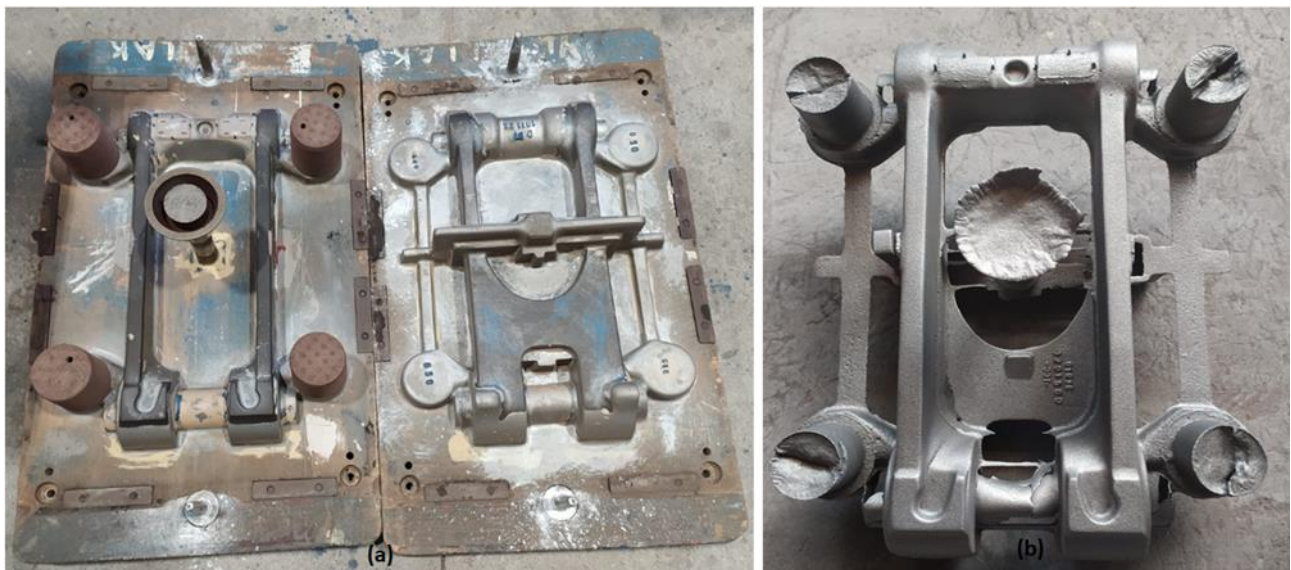


Figure 3. (a); The Image of the designed pouring system mounted to the part model, **(b);** The image of the poured part with designed pouring system

The part poured with the designed pouring system was examined and then a design change was made in the part solid data. In the casting part design, Stelex Pro $\varnothing 70 \times 22$ mm 10 PPI SiC-based filter was placed inside the KSE 8/11 exothermic feeder and the filling point of the casting part was revised as the kalpur direct pouring system. The kalpur direct pouring system was placed at the cope side in the casting part solid data and flow and solidification of the part was simulated at 1350 °C by choosing lip pouring ladle. According to simulation results, the kalpur direct pouring system was mounted to the casting part model. Images of the simulation results of the casting part are shown in Figure 4, and the kalpur direct pouring system is shown in Figure 5.

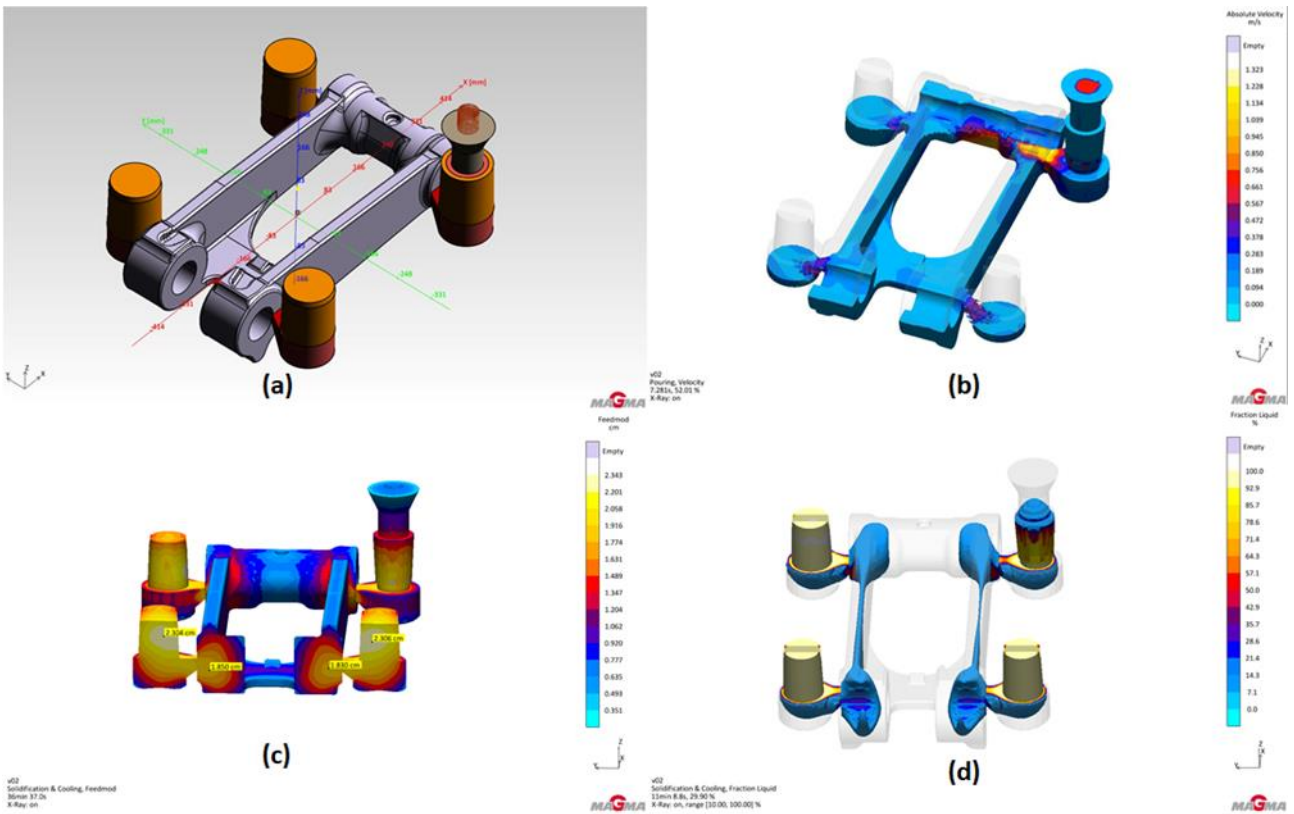


Figure 4. (a); The image of the casting part geometry, (b); The image of the metal flow and filling simulation of the casting part, (c); The image of the feeding mod of the casting part, (d); The image of the friction liquid mod of the casting part

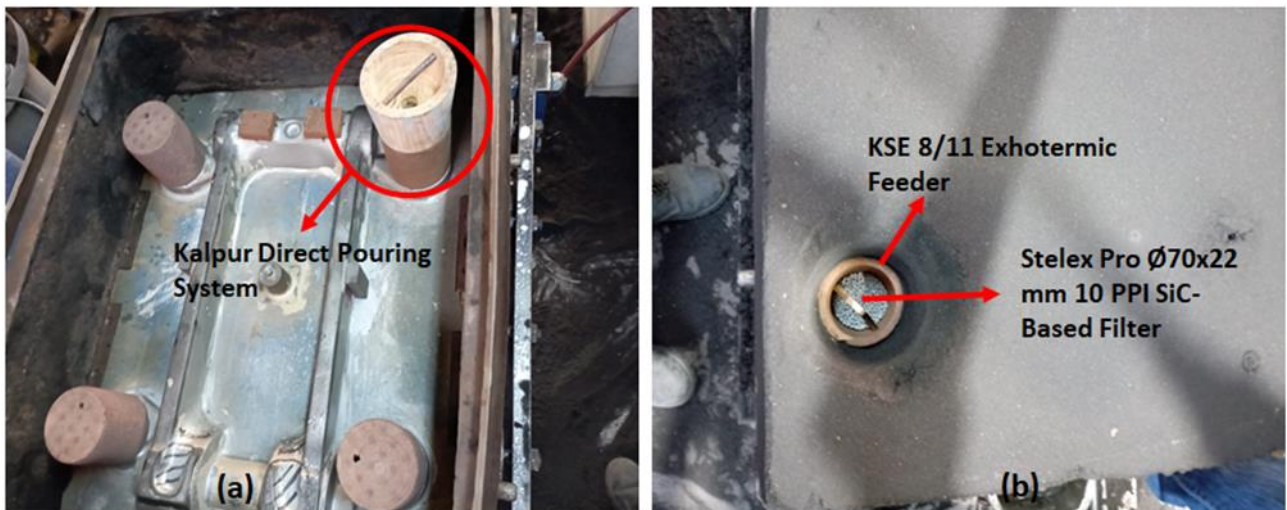


Figure 5. The Image of the kalpur direct pouring system

After simulation results, one part was molded in the greensand molding system in ÇİMSATAŞ foundry and the casting was carried out with a lip pouring ladle at 1350 °C and in 15 seconds. Total gross weight of the casting part has been detected as 96 kg. Images of the poured part with the kalpur direct pouring system are shown [Figure 6](#).

3. Results

In this article, the casting parts have been designed according to the simulation results with different pouring system versions by using the material GGG50 ductile iron castings. The findings were obtained from the simulations results and the results of the poured parts.

- It was found that the simulation results represented nearly the actual casting results.
- The total gross weight of casting part poured with kalpur direct pouring system has decreased from 105 kg to 96 kg.

- It was observed that the yield of the poured part with the designed pouring system was 56.2% and the yield of the poured part with the Kalpur direct pouring system was 61.66%.
- While 4 cores were used in the first designed pouring system, only 2 cores were used in the kalpur direct pouring system. 2 cores have been eliminated in the molding of the casting part by the kalpur direct pouring system.
- It has been observed that clean part can be poured with the gating system ratio of 1:3,5:2,5.
- While the filling time of the poured part with the designed pouring system was 20 seconds, the filling time of the poured part with kalpur direct pouring system was decreased to 15 seconds.
- It has been observed that the surface qualities of the poured parts are close to each other in both pouring systems.



Figure 6. The image of the poured casting part with the kalpur direct pouring system

4. Conclusion

It has been observed that designed pouring system with ratio of 1:3,5:2,5 for GGG50 ductile iron castings minimizes the escape of the non-metallic inclusions from ladle into the casting part during filling of the molten metal to the mold cavity. In addition, it has been increased the importance of the use of ceramic foam filters in foundries in recent years.

By using the design of the different version of the pouring systems in the ÇİMSATAŞ foundry, the surface quality of the casting part has improved by design of both pouring systems. It has been seen that ceramic foam filters are cost-effective and efficient way to reduce casting defects.

Acknowledgement

We would like to thank ÇİMSATAŞ General Manager Mr. Fatih ERDOĞAN, ÇİMSATAŞ Production Group Manager Mr. Necmettin ACAR, ÇİMSATAŞ Foundry Manager Mr. Kazım ÇAKIR, ÇİMSATAŞ Foundry Production Chief Mr. Buğra ERBAKAN, ÇİMSATAŞ Production Engineer Mr. Vedat UZ, ÇİMSATAŞ Foundry Finishing Engineer Mr. Mert DEMİRDÖĞEN, ÇİMSATAŞ Foundry Production Foreman Mr. Sabahattin KAYA, ÇİMSATAŞ Foundry Finishing Foreman Mr. Erdal YALÇIN, ÇİMSATAŞ Foundry Finishing Foreman Mr. Halil Deniz ÇOBAN, ÇİMSATAŞ Foundry Model Shop Foreman Mr. Ahmet AVCI, FOSECO Simulation Engineer Mr. Volkan EVNİ, and FOSECO Sales Engineer Mr. Halis ARTUT.

This study was partly presented at the 5th Advanced Engineering Days [17].

Funding

This research received no external funding.

Author contributions

Mustafa Murat Zor: Conceptualization, Methodology, Software, Data curation, Writing-Original draft preparation, Software, editing, **Serdar Kesim:** Validation, **Ferhat Tülüce:** Validation, Editing, **Alper Yoloğlu:** Data curation, Editing

Conflicts of interest

The authors declare no conflicts of interest.

References

1. Campell, J. (2015). *Complete Casting Handbook*, 2nd ed., Butterworth-Heinemann, Oxford.
2. Campell, J. (2004). *Casting Practice The 10 Rule of Castings*, 1st ed., Butterworth-Heinemann, Oxford.
3. Campbell, J. (2012). Stop pouring, start casting. *International Journal of Metalcasting*, 6(3), 7-18.
4. Melendez, A. J., Carlson, K. D., & Beckermann, C. (2010). Modelling of reoxidation inclusion formation in steel sand casting. *International Journal of Cast Metals Research*, 23(5), 278-288.
5. Renukananda, K. H., & Ravi, B. (2016). Multi-gate systems in casting process: comparative study of liquid metal and water flow. *Materials and Manufacturing Processes*, 31(8), 1091-1101.
6. Brown, J. (Ed.). (2000). *Foseco ferrous foundryman's handbook*. Butterworth-Heinemann.
7. Zor, M. M., Yoloğlu, A., Kesim, S., & Tülüce, F. (2022). Pressurized gating system design and optimization in steel castings. *Engineering Applications*, 1(1), 1-10.
8. Modaresi, A., Safikhani, A., Noohi, A. M. S., Hamidnezhad, N., & Maki, S. M. (2017). Gating system design and simulation of gray iron casting to eliminate oxide layers caused by turbulence. *International Journal of Metalcasting*, 11(2), 328-339.
9. Janiszewski, K., & Kudliński, Z. (2006). The Influence of Non-Metallic Inclusions Physical State on Effectiveness of the Steel Filtration Process. *steel research international*, 77(3), 169-176.
10. Sedex (1999). Foseco Foundry International, the Ceramic Foundry Filter with Foam Structure. Staffordshire, England.
11. Hsu, F. Y., Jolly, M. R., & Campbell, J. (2009). A multiple-gate runner system for gravity casting. *Journal of Materials Processing Technology*, 209(17), 5736-5750.
12. Janiszewski, K. (2013). The slenderness ratio of the filter used in the process of liquid steel filtration as the additional parameter of the filter form. *steel research international*, 84(3), 288-296.
13. Ogawa, K., Kanou, S., & Kashihara, S. (2006). *Fewer Sand Inclusion Defects by CAE* (Vol. 52, No. 158, pp. 1-7). Komatsu Technical Report.
14. Hrabina, D. (2016). Effective Filtration of Steel Castings, 7th International Ankiros Foundry Congress, 11-13 September, Istanbul, Turkey
15. Jezierski, J., Dojka, R. & Jenerka, K. (2017). Optimizing Gating System for Steel Castings, 5th International Conference on Modern Manufacturing Technologies in Industrial Engineering, 14-17
16. Zor, M. M., Kesim, S., Erbakan, B., Tülüce, F., Yoloğlu, A., & Çakır, K. (2022). Direct pouring system design and optimization in steel castings. *Engineering Applications*, 1(2), 124-131.
17. Zor, M. M., Kesim, S., Tülüce, F., & Yoloğlu, A. (2022). Reducing casting defects in ductile iron castings by optimized pouring system. *Advanced Engineering Days (AED)*, 5, 25-28.



© Author(s) 2023. This work is distributed under <https://creativecommons.org/licenses/by-sa/4.0/>